



Silk: history, obtaining, structure and properties of an old material in the development of new technologies

Roberta S. Pugina¹; José Maurício A. Caiut²;

*Corresponding author: E-mail address: caiut@ffclrp.usp.br

Abstract: For thousands of years, the silk produced in the *Bombyx mori* glands and used in the preparation of cocoons has been employed in the textile industry to produce fabric. These cocoons consist mainly of fibroin (SF – silk fibroin), a fibrous protein with unique mechanical properties and which is biocompatible, biodegradable, and inexpensive. SF can be extracted from the cocoons by processing in aqueous medium, and it can be employed to obtain materials for different applications, including biomaterials for body implants, scaffolds for tissue engineering, and materials for photonic devices such as sensors, waveguides, and lasers.

Keywords: Silk. Fibroin. Applications.

Introduction

Silk is a natural and semicrystalline polymer with high malleability, unique mechanical properties, and superior tenacity as compared to any currently employed synthetic fiber.^{1,2} For thousands of years, since silk was discovered in China in the middle of 2600 BC, the textile industry has explored this material in its natural form.³ Silk is produced in specific glands called sericogenic glands. Some invertebrates spin it into the fiber form during metamorphosis, but silk composition will depend on source.^{4,5} The silk from silkworm (*Bombyx mori*) is the most produced and commercialized. It consists chiefly of fibroin and sericin proteins, and *Bombyx mori* uses it to manufacture the cocoons, to which fibroin and sericin acids provide resistance and protection, respectively.^{2,6} Sericulture refers to the cultivation of silkworm. This culture was spread in Brazil in the beginning of the last century. It occurs mainly in the state of Paraná, in the so-called Vale da Seda paranaense, where silk threads are produced and exported to several countries.^{7–9} However, in the 1940s, fibroin, a fibrous protein and a major component of the silk thread, started to arouse scientific interest. Structurally, this protein consists of two chains, one ~25-kDa chain and one ~325-kDa chain.⁶ The largest chain comprises distinct regions known as silk I and silk II, which present different degrees of crystallinity.¹⁰ Fibroin can be extracted from silk threads by degumming, a low-cost process that requires water.² The solution obtained after this process can be used to develop numerous materials such as films, fibers, and spheres, among others. Additionally, the solution can be submitted to several treatments, to give a series of products;² e.g., silk sutures,^{6,11} which have been employed

for decades. Moreover, the solution can be used to obtain biomaterials, including implants and scaffolds for tissue engineering^{12,13} as well as photonic devices like sensors, waveguides, and lasers.¹⁴ Silk-based materials have the advantage of being biocompatible,^{2,12,13} biodegradable,¹⁵ resorbable,¹⁶ and mechanically robust¹, among other characteristics, which allows them to be widely applied and opens various possibilities for their use in countless areas. In addition, the cocoons can be obtained as waste from the textile industry, which reduces the cost of producing new materials.

History

The story that describes the discovery of silk by humanity is full of legends and divergences.³ According to the account of the Chinese thinker and philosopher Confucius (571–479 BC), the most accepted to date, in 2640 BC silk was accidentally discovered by the Chinese Empress Hsi-Ling-Shi, wife of Emperor Huang Di (or Huang-Ti), also known as the “Yellow Emperor”, who is thought to have ruled China from 2697 to 2597 BC, before the Xia dynasty. Legend has it that silk was discovered while the Empress was drinking a cup of tea under a mulberry tree—a cocoon fell into her cup and, upon contact with the hot water, it broke apart, revealing the fiber produced by silkworm.^{3,17–19} Moved by curiosity, Hsi-Ling-Shi would have managed to transform that material into a piece of fabric and slowly started the weaving process, which is practically the same as the one used today. Although the textile industry was established at that time, it only peaked around 1500 BC, during the Shang dynasty. In the two following millennia, the Chinese were the exclusive

¹ Departamento de Química, Faculdade de Filosofia, Ciências e Letras de Ribeirão Preto, Universidade de São Paulo, Ribeirão Preto – SP, Brazil

manufacturers and exporters of silk: being aware of the commercial value of the fabric, the Chinese government banned mulberry seeds and silkworm eggs from being exported and threatened those who disrespected the ban with the death penalty.^{3,20}

However, the ban was bypassed in 552 of the common era, when Justinian, the Roman Emperor, sent monks in disguise on a spy mission to China, to hide silkworm eggs in their luggage and take them to Constantinople inside bamboo sticks. As a result, the capital of the Roman empire at the time, present-day Istanbul, became the first European silk center, and this episode marked the arrival of sericulture in the Western World and the beginning of its dissemination to all continents in the following centuries. Due to its lightness, brightness, and beauty, silk, like precious stones and gold, has always been treated as a valuable object. The high commercial interest in it motivated the creation of the largest commercial route in the world, the so-called “Silk Road”, leading to the foundation of great civilizations.^{3,20} This path, which was the most important cultural and commercial link between the West and the East for hundreds of years, only received the name of “Silk Road” in the 19th century. Even though many products have been sold and traded along it, the one with the greatest prominence and attracting the most attention has always been the Chinese fabric, which led the German traveler and geologist Ferdinand Freiherr to name the path “Silk Road” (from the original “Die Siedenstrasse”, in German).^{3,21–24}

In Brazil, the history of silk fabric production began centuries later. In this country, the first mulberry trees were apparently grown in the middle of the 18th century in the state of Minas Gerais, as demanded by Queen Dona Maria I (also called “The Pious” and “The Crazy”), who ruled Portugal and Brazil at the time, until she was considered mentally incapable. However, although Brazil already had the basic subsidies for the cultivation of silkworm, silk fabric production only started in the Second Empire (1850). This is because Portugal had an agreement with England that forced the Portuguese colonies to import English fabric, thereby delaying the emergence of the Brazilian textile industry. In fact, this industry only developed after the Second World War, in the second half of the 20th century. Nevertheless, today Brazil is the fifth largest producer of silk fabric in the world. China still dominates the market, accounting for almost half of the silk fabric production on the planet. Even though Brazil remains behind China, India, Uzbekistan, and Thailand, the Brazilian silk fabric industry stands out for the quality of its yarns, produced mainly in the state of Paraná.^{3,23,24}

Production and obtainment

Obtaining silk on a large scale is only possible thanks to sericulture, the part of zootechnics that deals with the study and development of silkworm (Kingdom: Animalia,

Phylum: Arthropoda, Clade: Pancrustacea, Order: Lepidoptera, Genus: *Bombyx*, Species: *Bombyx mori*).^{25,26} Sericulture is a thorough process that has been carried out pretty much the same way since silk was discovered approximately 4,500 years ago. It is the oldest known agroindustrial activity, and it is currently practiced by approximately 40 countries.¹⁸ The so-called “Silk Farms” are in fact small family productions that operate without the need for advanced technologies given the delicacy of the cocoons produced therein. Therefore, production can be implemented in small areas and is promising for the social and economic development of rural areas. This activity keeps producers in the countryside, and it depends on some factors, especially climatic ones.⁷ In Brazil, the only Western country that produces silk on a commercial scale, production began in the 19th century, in the state of São Paulo. Sericulture is integrated with the industry and employs approximately 8,000 families. These families receive the eggs – supplied by companies specialized in the production of yarns – to cultivate silkworm and to obtain the cocoons. These families also grow mulberries (*Morus* sp) to feed silkworm. Indeed, silkworm feeds on the leaves of these plants, which must be grown isolated and without pesticides, so as not to interfere in the quality of the silk threads. In Brazil, this activity is currently concentrated in the state of Paraná, as already mentioned. More specifically, it occurs in the so-called Vale da Seda paranaense, which comprises 29 cities.^{7–9,18,27} This activity started there in 1950 and, 30 years later, this region became the largest national producer, with about 53% of all the Brazilian silk production. This percentage increased to 90% in the 1990s and has remained so until today. The largest share of silk production is exported to textile industries worldwide. To ensure the quality of the yarns produced nationally, local producers select and use only high-quality cocoons; the others (10 to 20% of all the production) are discarded.^{7,8} Silk is composed of natural proteins²⁸ produced in specific glands called sericogenic glands. It is spun into fibers by invertebrates such as mites, moths, spiders, and silkworm;⁵ its composition depends on the source. The best-known and best-characterized silks originate from silkworm (*Bombyx mori*) and spiders (*Nephila clavipes*),^{5,29–31} which stand out for their strength and hardness.³² However, spiders have predatory nature and low production,⁶ so the silk produced by them is not commercialized very frequently. On the other hand, silk production by silkworm is expressive and occurs through sericulture.

Silkworm uses silk to produce the cocoons, where it lives until it undergoes metamorphosis and becomes a moth. Silkworm development comprises four stages – egg, larva, pupa, and moth – and lasts around 60 days. In the first step, around 300–400 eggs are deposited by the female moth at a time; the moth dies almost immediately after egg deposition. Fourteen days later, these eggs

hatch into larvae. The larval stage lasts approximately 27 days and comprises five stages, during which the larvae feed on mulberry leaves and begin to prepare the cocoon, a process that takes approximately four days and which is carried out by using a single wire measuring between 700

and 1500 m long. Once this is done, silkworm moves to the pupal phase, where it remains for 14 days, inside the cocoon. Finally, it turns into a moth, which lives for seven days.³³⁻³⁵ Figure 1 illustrates these steps.

Figure 1 – Representation of the *Bombyx mori* life cycle.


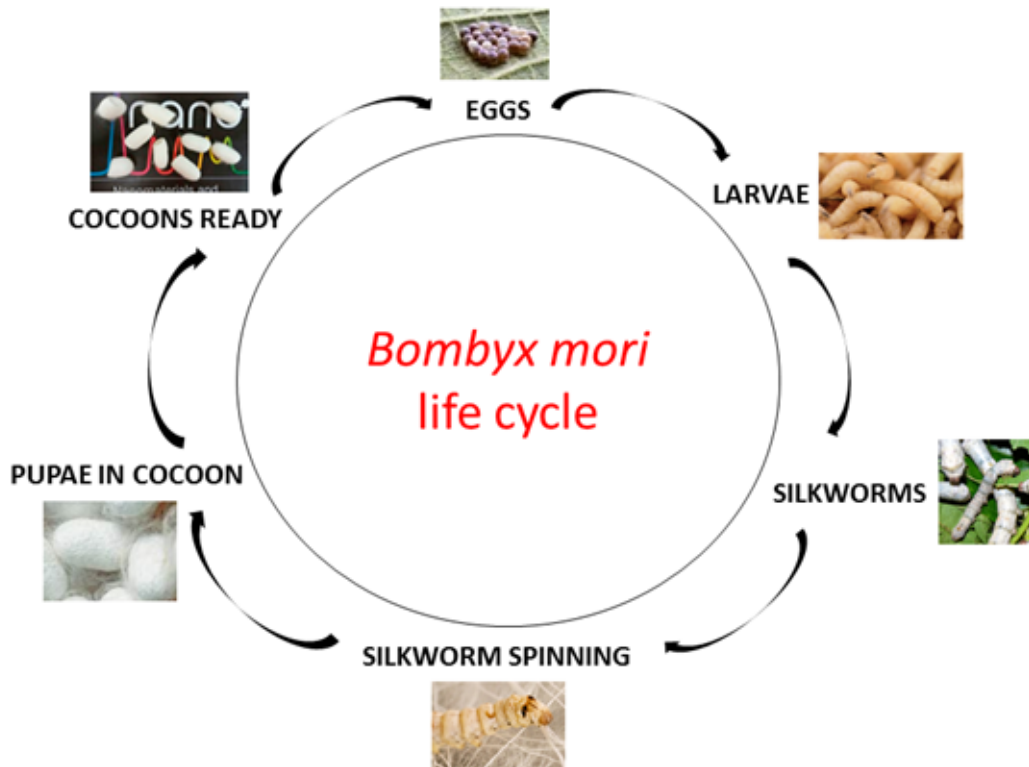


Figure 2 – Representative scheme of the composition of silk threads.

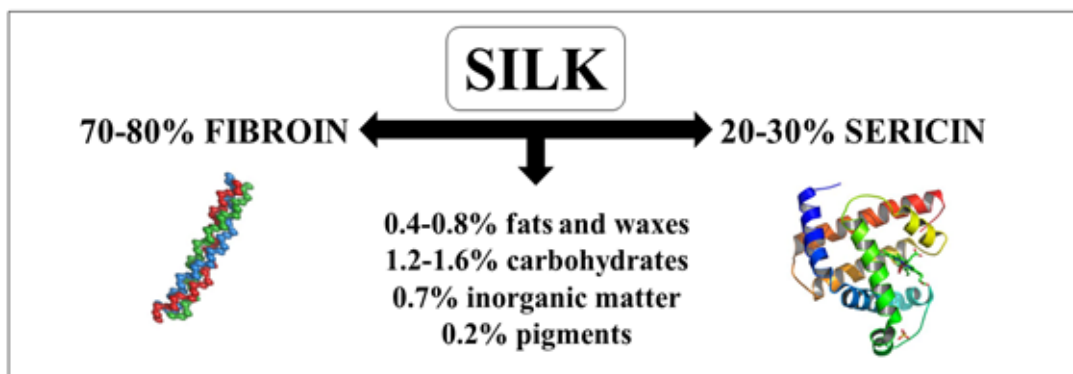

The textile industry is interested in the cocoons. Starting from the egg, the estimated time for obtaining them is approximately 45 days. These cocoons consist mainly of two proteins: fibroin (~70%), which belongs to the fibrous class and provides the cocoons with resistance, and sericin (~30%), which belongs to the globular class and provides the cocoons with protection.² There are also other materials³⁶, as shown in the scheme represented in Figure 2.

From a chemical standpoint, proteins are macromolecules built up from a set of 20 amino acids. The latter are smaller molecules bearing two functional groups – carboxyl and amino – in their structure.²⁸ In the case of the proteins constituting the main core of the silk thread, there is high percentage of glycine and alanine in fibroin and of sericin and threonine in sericin, as well as other subunits (in smaller proportions)³³. Please see Table 1.

Table 1 – Percentage of amino acids constituting the proteins present in the silk thread.³³

AMINO ACID	% in fibroin	% in sericin
Glycine (Gly)	42.8	8.8
Alanine (Ala)	32.4	4.0
Serine (Ser)	14.7	30.1
Tyrosine (Tyr)	11.8	4.9
Valine (Val)	3.0	3.1
Aspartic acid (Asp)	1.9	16.8
Glutamic acid (Glu)	1.7	10.1
Threonine (Thr)	1.2	8.5
Phenylalanine (Phe)	1.2	0.6
Isoleucine (Ile)	0.9	0.6
Arginine (Arg)	0.9	4.2
Leucine (Leu)	0.7	0.7
Proline (Pro)	0.6	0.5
Lysine (Lys)	0.5	5.5
Tryptophan (Trp)	0.5	0.5
Histidine (Hys)	0.3	1.4
Methionine (Met)	0.2	0.1
Cysteine (Cys)	0.1	0.3

Fibroin, the major component in the silk thread, is a protein of the fibrous class. It plays a structural role and constitutes the nucleus of the silk filaments, providing the cocoons with resistance. On the other hand, sericin is a protein of the globular class, which functions as a “glue” that unites two fibroin filaments, to form a silk thread that protects the cocoon.^{2,6,37}

Thus, silk is composed almost entirely of organic components.³³ Its production is sustainable given that this material can be processed in water.² Moreover, it is

edible (so it can be used in the food industry),^{38–40} it originates from natural sources, it is inexpensive,⁶ and it has outstanding mechanical properties. Indeed, it is one of the most resistant natural fibers,^{1,33,41} which allows it to be used in several other applications, inside or outside the textile industry. A considerable part of the cocoons produced during sericulture is discarded.^{7,8,42,43} Therefore, in the last decades, hundreds of studies aiming at reusing these cocoons in the textile industry itself or in the production of “less noble” products have been conducted. An example of such studies is the Brazilian project “Casulo Feliz”, created by the zootechnician Gustavo Augusto Serpa Rocha in 1988.⁴⁴ Alternatively, the discarded cocoons can be employed to develop cutting-edge technology based on isolation of the protein constituents of the cocoons.^{1,2,12–14,45,46}

Fibroin, the major component of silk: extraction, structure, and properties

Although the history regarding the use of silk as sutures is centuries old,^{6,11} it was in the mid–1940s that fibroin derived from cocoons aroused scientific interest. In 1947, the first academic article reporting the use of fibroin outside the textile industry was published.⁴⁷ Since then, the possibilities of using this protein have extended to several areas, such as tissue engineering.^{4,48} Fibroin has also been employed in the development of various types of biomaterials^{12,13} and photonic devices¹⁴. Today, it is one of the most applied natural fibers.

Compared to fibroin, sericin is still less often used due to biocompatibility and hypersensitivity issues.^{6,49} However, many studies have investigated the application of sericin in other areas⁵⁰ including the development of compounds with antioxidant and bactericidal properties.^{34,40,51} Sericin has also been employed in the prevention against UV rays,⁵² in the composition of cosmetics,⁵³ and in the food industry.⁴⁰ This protein is commonly known as the “binding” protein. It involves and assembles the fibroin fibers, thereby providing the cocoon with a structure.³² Because it is a globular protein consisting predominantly of the amino acids serine (Ser) and aspartic acid (Asp) (Table 1), sericin is highly hydrophilic and is highly soluble in hot water,⁵² which allows it to be removed from silk during the “degumming” process – the procedure through which fibroin is extracted from the silk threads, to give a solution of this fibrous protein.²

While the textile industry disassembles the cocoon built from a single thread to produce fabrics, degumming is a “reverse engineering” process that starts from the cocoon, to return to the original components, proteins and water, present in the silkworm sericigenic glands and which are spun to produce the cocoons.^{54,55} This protein splitting process comprises four steps: (I) separation of proteins and extraction of fibroin from the silk threads; (II) fiber dissolution; (III) dialysis to remove excess salt

from the medium; and (IV) centrifugation to remove impurities from the cocoons itself. At the end of these steps (shown in Figure 3), an aqueous, viscous, and yellowish solution (~5% mass/volume) is obtained. This solution must be kept at 4 °C and remains stable for approximately 30 days.²


In step (I), the cocoons are heated to 100 °C in an alkaline solution of sodium carbonate (Na_2CO_3). A salt-in effect takes place – the low concentration of salts increases the solubility of the proteins because the saline ions interact with the ionic charges of the proteins, increasing the effective charge and the amount of water molecules attached to the protein ionosphere.²⁸ As already mentioned, the silk thread consist of two fibroin filaments linked together by a natural “glue”, sericin. Sericin is a globular protein and is more soluble than fibroin. Thus, it is solubilized, becoming loose and remaining in

solution, while the fibroin fibers remain rigid.²

These now dried loose fibroin fibers undergo dissolution (II), which can be carried out in the presence of various organic solvents and/or aqueous solutions² such as $\text{CaCl}_2\text{-EtOH-H}_2\text{O}$,^{56,57} $\text{Ca}(\text{NO}_3)_2\text{-MeOH-H}_2\text{O}$,⁵⁸ $\text{LiBr-EtOH-H}_2\text{O}$,⁴¹ $\text{LiSCN-H}_2\text{O}$,⁵⁹ $\text{NaSCN-H}_2\text{O}$,⁶⁰ and $\text{LiBr-H}_2\text{O}$.² The latter is the most commonly used system. In this case, LiBr acts as a chaotropic agent. At high concentration in aqueous solution, LiBr “removes” the water molecules surrounding the fibroin molecules, thus affecting the stability of the native conformation of these macromolecules, weakening the hydrophobic effect.^{4,28}

After the fibroin fibers are completely dissolved, a yellow viscous gel is obtained. This gel is then dialyzed (III) against ultrapure water for 48 h. After this period, the solution is centrifuged (IV) at 3500 rpm, to remove impurities.²

Figure 3 – Photograph of the fibroin extraction process steps. (I) A sequence of three images showing cut cocoons, cocoons being heated in Na_2CO_3 solution, and loose fibroin fibers. (II) The first image shows dry fibroin fibers; the second image shows dissolved fibroin fibers after dissolution in LiBr solution. (III) Dialysis of the obtained solution.

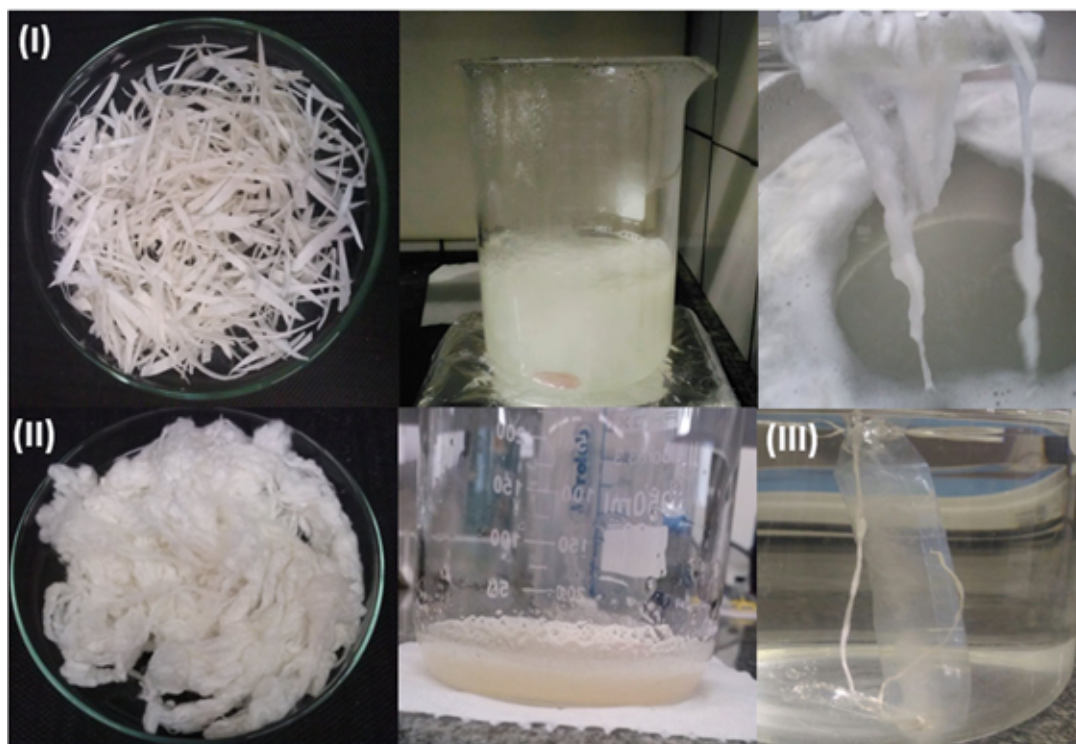


Structurally, fibroin consists of two chains: a larger one, with ~325 kDa (H) –chain), and a smaller one, with ~25 kDa (L) –chain)⁶. These chains are linked by a disulfide bond formed between two cysteine residues,⁷¹ leading to an HL complex, which at the same time is also non-covalently linked to a P25 glycoprotein (~25 kDa). The whole structure of this protein^{62–64} was first characterized by Marsh in collaboration with Corey and Pauling in 1955.⁶⁵ The high-molar-mass region underlying the tension properties of fibroin is a crystalline structure composed by repetitions of the amino acids that build up its primary structure (in that order Gly – Ala – Gly – Ala – Gly – Ser) and which may have the so-called silk I and silk II. Silk I is a hydrophilic, less crystalline region consisting of alpha-helix structures or random coil; silk II is hydrophobic and is more crystalline due to the presence of antiparallel beta-leaves.¹⁰ Silk I can be converted to silk II by specific treatment with methanol. In addition to these two regions, a small and unstable structure, known as silk III, may occur at the air/water interface of the fibroin in solution, but its structure has been less explored.⁶⁶ The low-molar-mass chain accounting for chemical resistance and moisture retention is an amorphous, hydrophilic structure that does not present the repetition of the amino acids that build up the primary structure.^{62–64,67–71}

Fibroin comprises 5263 amino acid residues; Gly, Ser, and Ala are the main constituents of the primary structure, whereas other residual amino acids exist in smaller proportions,^{72,73} as shown in Table 1.

Because fibroin belongs to the fibrous class and presents many hydrophobic amino acid residues in its structure, it is a water-insoluble protein.³³ As mentioned previously, this protein has unique characteristics that allow it to be used in several areas. Among these characteristics, its biocompatibility,^{6,12,13,48} biodegradability,¹⁵ resorbability,¹⁶ high mechanical resistance,^{1,74} relative stability to the environment it occupies,⁶ flexibility,⁷⁵ ability to self-crystallize⁶² and to self-organize,² structural functionality,^{2,76,77} possible coordinative environment for ions or molecules of interest,⁷⁸ permeability to vapors of interest,⁸⁰ transparency in all the visible spectrum, smooth surface, and variable refractive index^{81–83} stand out.

After sericin is completely removed from the silk thread, the resulting fibroin solution can be used to prepare different materials, which is promising for several applications. Some designs are illustrated in Figure 4 and include gels, fibers, films, microspheres, tubes, and sponges. The time required to obtain these materials varies from one to five days,² depending on the method.

Figure 4 – Scheme of the numerous shapes that can be obtained from the fibroin solution. The number of days that are necessary to obtain each shape is counted only after the fibroin solution is prepared.²

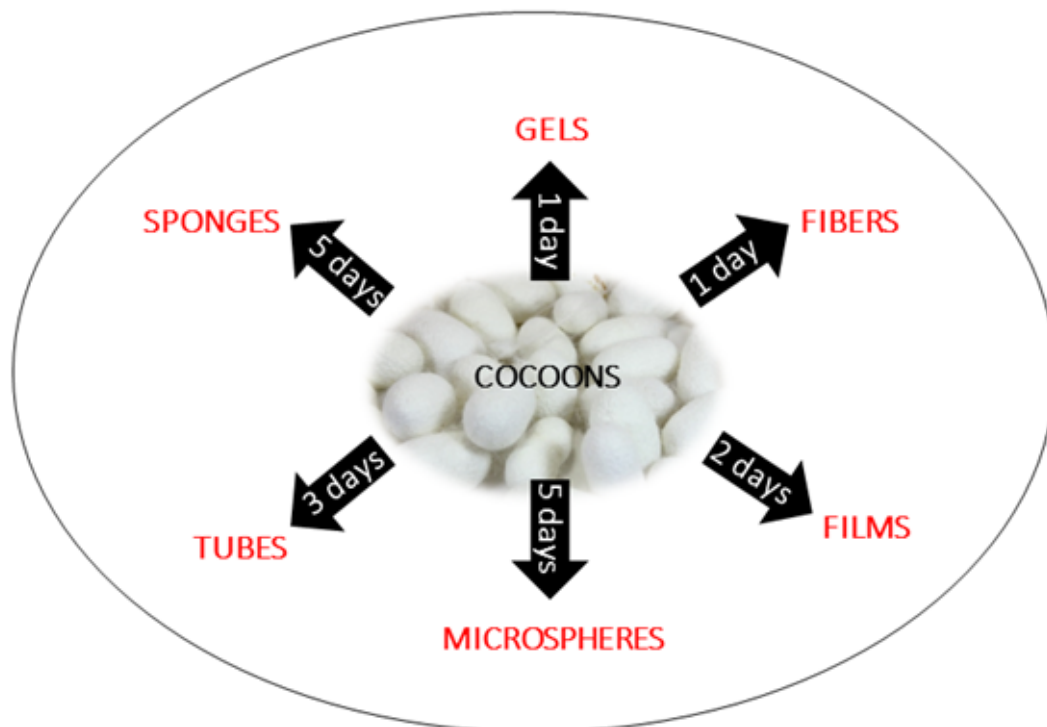

The fibroin crystalline structure, and hence its mechanical properties, can be modified during the preparation of these materials, by altering the fibroin concentration in the solution, the solvent used during treatment (water or alcohols), and the treatment temperature⁸⁴ and by adding other components or creating/distributing pores.^{2,4,6,12,14,76,85,86} The thickness and degradation time for materials such as films and tubes can be controlled by changing the fibroin concentration in the solution used during the preparation.^{2,87} Through a simple drying process in ambient conditions, insoluble materials, like films, can be obtained – beta sheets (conversion of silk I to silk II) are formed as a result of water removal. However, the materials obtained by this method are brittle, but this can be improved through treatment with hot water or methanol.^{4,76,88–90} Treatment with water vapor only affords more flexible materials that degrade within a shorter time than materials treated with methanol, a widely used method for preparing materials of different shapes, such as spheres and fibers.² In addition to the previously mentioned films and tubes, because methanol can induce fibroin crystallization, a larger number of beta-sheet structures arise.^{76,89,90} In general, treatments with water vapor only give a smaller amount of beta sheets than treatment with alcohol, such as methanol. A small number of beta sheets results in less crystalline, more malleable, and softer materials, whilst an increase in the number of these structures affords more crystalline and rigid materials.⁷⁶

Besides these treatments, the mechanical properties of fibroin can be improved by adding other components;^{91–95} for example, fibroin blends with acrylic polymers,⁶⁰ polysaccharides,⁹⁶ collagen,⁹⁷ and sodium alginate,⁹⁸ among others, can be obtained.^{99,100} Porous materials can also be achieved by using polyethylene oxide (PEO)², thus creating matrixes with defined porosity and modified surface properties.^{101–103} Another factor that can influence the properties of the resulting materials is the age of the cocoons that are used to obtain the fibroin solution, as demonstrated by Ramirez and collaborators.¹⁰⁴

Film is one of the simplest forms into which fibroin can be molded. To prepare a film, the typical feature of proteins must be considered: these macromolecules tend to self-organize as they spread over a surface. Therefore, they acquire the shape of the surface after the solvent present in the protein solution, in this case water, is evaporated under ambient conditions (dry casting).^{2,4,105} In this way, non-patterned or patterned fibroin films can be achieved by changing only the substrate where the film is prepared. The choice of substrate will depend on the target application given that this film will “load” the cha-

racteristics of the substrate. Apart from this preparation method involving manual deposition, these materials can be obtained by other techniques, such as layer-by-layer (LbL) deposition,^{74,86,106–108} which produces ultrafine fibroin films, as well as spin coating,^{109,110} Langmuir-Blodgett (LB) process,^{66,111,112} and others.⁴

Fibroin tubes can also be obtained by a simple method like dip coating, by immersing a template in a solution with high fibroin concentration, as described by Rockwood and collaborators.² After immersion, the system must be homogenized and placed in contact with methanol, which can induce formation of beta-sheet structures and stiffen the material.^{4,76} After treatment, the templates with the solution are dried at room temperature. This method enables tube thickness to be controlled through control of the fibroin concentration in the solution and the number of layers deposited on the template;^{2,115} furthermore, porous tubes can be created.¹¹³ Another methodology involves spinning gel (gel spinning).¹⁰²

Wenk and collaborators¹¹⁴ obtained fibroin microspheres by a method that uses mild conditions and a vibrating mouthpiece. In this system, the fibroin solution is added with a syringe and ejected in the form of drops by action of the mouthpiece with controlled vibration and frequency. The drops are poured into a reservoir containing liquid nitrogen and solidify upon contact with it.

Spherical fibroin materials can also be prepared by other methods. For instance, fatty acid lipids (DOPC: 1,2-Dioleoyl-sn-glycerol-3-phosphocholine) can be employed to encapsulate the aqueous fibroin solution. The fatty acid lipids can be in the pure form or in the presence of a molecule of interest, which act as a template. After vesicles are generated, the lipid can be removed, and the resulting spheres are resuspended. In the case of DOPC, which is soluble in methanol and can stiffen fibroin, methanol is used to remove the lipid.^{2,115} Phase separation between the aqueous fibroin solution and another polymer, such as PVA (polyvinyl alcohol), is another useful method that is simple and dismisses the use of other solvents.^{2,116}

Fibroin fibers are generally obtained by electrospinning, a process that affords materials with large surface area and reduced diameter.^{117–122} This methodology is widely employed due to the simplicity of the experimental electrical force apparatus – it basically consists of three components, syringe, high voltage source, and collector – not to mention its high efficacy and low cost.^{2,117}

Fibroin is also widely used to produce three-dimensional scaffolds with controlled morphology and porosity. These scaffolds can be obtained from gel, hydrogels, or sponges. Sponges can be achieved by adding and subsequently removing salts from the fibroin solution in aqueous medium; pore size can be controlled.^{2,123} In addition to this aqueous method, sponges can also be prepared by using organic solvents, like the alcohol HFIP

(1,1,1,3,3,3-hexafluoro-2-propanol).^{2,124}

Finally, hydrogels can be prepared by a series of methods involving decreasing the pH value of the medium,¹²⁵ sonication¹²⁶, or application of an electric current.¹²⁷ In all cases, the material is produced in a simple and fast way, and the choice of method will depend on the target application.² Nogueira et al.¹²⁸ demonstrated that these materials can be achieved by fibroin solution dialysis at different temperatures, without the need for further treatments, constituting another simple and effective route that affords promising structures for biological applications.

Applications

Because fibroin provides positive responses due to its biocompatibility,^{2,12,13,48} among other properties, it has been widely explored for the development of diverse biomaterials in the medical field for decades;^{12,13} moreover, it has promising use in the development of photonic devices.¹⁴ Among the possible applications of this natural polymer, we can mention its use in drug delivery systems,^{115,130-135} as scaffold in tissue engineering for repair of tissues (such as cornea¹³⁶⁻¹⁴⁰ and vascular^{102,113,141-144} and bone¹⁴⁵⁻¹⁵⁴ tissues), and as dressing for healing skin lesions.¹⁵⁵⁻¹⁵⁸ Other application areas include cancer diagnosis and treatment,¹⁵⁹ photodynamic therapy,¹⁶⁰ enzyme immobilization,¹⁶¹⁻¹⁶⁶ photonic devices,^{16,167} lasers,¹⁶⁸⁻¹⁷⁴ biosensors,¹⁷⁵⁻¹⁸⁰ waveguides,^{72,181,182} fuel cells,¹⁸³ energy storage devices,¹⁸⁴ and materials with antithrombotic properties.^{185,186}

Drug delivery

Controlled drug delivery using implantable biopolymers offers numerous advantages over conventional methods. Advantages include controlled and constant administration at the required therapeutic rate without peaks or valleys.^{187,188} The release rates are determined by the vehicles themselves. The vehicles must be biocompatible and amenable to large-scale production, and they must work for days or even years.¹⁸⁷ In this scenario, carrier materials based on fibroin stand out for their biocompatibility, excellent mechanical properties, controlled degradation through crystallinity control (quantity of beta-sheet structures), ability to immobilize enzymes, and other therapeutic properties. Besides that, they can be processed in mild conditions and molded into different shapes.¹²⁹⁻¹³⁵

Through the most diverse forms, fibroin-based materials can be used to encapsulate/release a series of molecules and bioactive compounds. For example, Wang and colleagues prepared carrier microspheres in the presence of lipids and subsequently treated them with methanol and sodium chloride solution, to obtain materials with different surface characteristics, for different applications.¹¹⁵

Moraes and collaborators prepared fibroin hydrogels in the presence of diclofenac molecules for controlled delivery of this compound. They dissolved the drug in water or ethanol and later added it to fibroin, to obtain carrier hydrogels. In the case of the drug dissolved in water (SF-H₂O), hydrogel formation took three days, but this time decreased to 10 minutes for the drug dissolved in ethanol (SF-EtOH), confirming that ethanol accelerated the gelling kinetics. The authors studied the delivery profile of the drug in the two cases, under the same conditions. For SF-EtOH, drug release was faster at the beginning of the experiment and reached equilibrium after 10 h, whereas equilibrium was reached after 5 h in SF-H₂O. The data suggested that hydrogels containing diclofenac dissolved in ethanol presented more sustained controlled delivery because the SF-EtOH hydrogel emerged more rapidly and in the presence of well-organized beta-sheet structures, resembling cross-linking processes, thereby resulting in more controlled diclofenac release.¹³²

Among the possible applications of carrier systems, tissue engineering to induce the growth of tissues like the cornea and vascular, bone, and skin tissues stand out.¹³³

Through the most diverse forms, fibroin-based materials can be used to encapsulate/release a series of molecules and bioactive compounds. As an example, Wang and colleagues demonstrated the preparation of carrier microspheres in the presence of lipids and subsequent treatment with methanol and sodium chloride solution, where it was possible to obtain materials with different surface characteristics, widening the use for different purposes¹¹⁵.

Moraes and collaborators have shown the preparation of fibroin hydrogels in the presence of diclofenac molecules with potential use in controlled delivery of this compound. In this research, the drug was dissolved in water and in ethanol, and later added to fibroin to obtain carrier hydrogels. As for the drug dissolved in water (SF-H₂O) the time required to obtain the hydrogel was 3 days, while in the case of dissolution in ethanol (SF-EtOH) the gelation time decreased to 10 minutes, confirming the effect of acceleration on the gelling kinetics by ethanol. The delivery profile of this medication in the two mentioned cases was studied under the same conditions as shown in Figure 7. In Figure 7 is also possible to notice that for SF-EtOH the drug release occurred more quickly at the beginning of the experiment and reached equilibrium after 10 h. On the other hand, in SF-H₂O the equilibrium was reached after 5 h. According to the researchers, the data presented suggest that hydrogels containing diclofenac dissolved in ethanol present a more sustained controlled delivery compared to those obtained with the drug dissolved in water. This can be explained by the fact that the SF-EtOH hydrogel formation occurred more rapidly and in the presence of well-organized beta-sheet structures, similar to what occurs in cross-linking processes, thus,

resulting in a more controlled release of this medication¹³²

Among the possible applications for carrier systems, the most studied and explored is in the area of tissue engineering in inducing the growth of the most diverse types of tissues such as the cornea, vascular, bone, and skin tissues¹³³.

Tissue Engineering

Tissue engineering, a sub-area of biomedical engineering, is an interdisciplinary area that gathers knowledge from several fields to develop systems that can act in the maintenance, restoration, or performance improvement of different organs and tissues. Therefore, this sub-area requires the use of biocompatible matrixes that can receive bioactive cells or molecules and later be implanted at the destination site, where they adapt to the microenvironment and mimic the damaged area. The resulting arrays are commonly called "scaffolds". Apart from the minimum biocompatibility requirement expected for these materials, their degradation time along with the regeneration time of the tissue in which they are inserted also determines their application. In the search for biomaterials that can act in the reconstruction of tissues, structural proteins such as collagen, elastin, and albumin stand out for being natural and easily found components.^{2,4,6} In this context, silk fibroin has been increasingly explored due to its elasticity properties, mechanical resistance, controlled biodegradation, and biocompatibility.^{4,189–196}

The most reported tissues for potential regenerative treatments using fibroin-based materials, whether pure or in the presence of other compounds,¹⁵³ are bone (36%),^{145–154} cartilaginous (17%),^{197–203} vascular (10%),^{102,113,141–144} and cutaneous (5%) tissues,^{155–158} as well as cornea (2%)^{136–140}, as described by Kasoju and Bora in 2012.¹⁸⁹

Compared to other types of tissues, fibroin has been mostly employed in bone repair.¹⁸⁹ Bone tissue is made up mainly of hydroxyapatite and collagen, and it can be recovered by inducing osteoblast cell proliferation. Since the role of fibroin as a biomaterial was first reported in 1995,²⁰⁴ many studies have been carried out, and bone regeneration using this material in the form of fibers obtained by electrospinning,¹⁵² of hydrogels,^{146–149} of porous membranes,¹⁵¹ of films in the presence of hydroxyapatite,¹⁴⁵ as well as functionalized with other molecules^{205,206} has already been successfully demonstrated.

Two decades ago, Sofia and collaborators²⁰⁵ reported images of the systems they prepared. The images were obtained by calcein fluorescence and showed maximum calcification in the fibroin and RGD (peptide sequence) substrate after four weeks. These results supported the concept that fibroin can induce bone tissue growth, especially when it is functionalized with molecules of interest.

Skin dressing

Due to their biocompatibility, low immunogenicity, and nontoxic and non-allergenic nature, biopolymer dressings have been widely used in the treatment of skin lesions.²⁰⁷ The mechanism through which these lesions are recovered occur in different parts of the skin and is complex: it involves various types of cells and requires a material with good adhesion.²⁰⁸ Therefore, materials that can incorporate and carry molecules, like drugs, in their structure and which can be molded in different ways have gained prominence in this area.²⁰⁷ Fibroin-based materials have been investigated as dressings for skin wound healing since the 1990s. These materials are effective substrates for proliferation of adherent cells and can be an alternative to replace collagen.²⁰⁹ Indeed, studies have shown the effectiveness of materials based on pure fibroin^{210,211} and of materials obtained through previous treatments and as blends in the presence of other compounds.^{155–158}

Vasconcelos and collaborators prepared fibroin and elastin compounds via freeze-drying and proved that they effectively induced the recovery of wounds caused by skin burns. The combination of the self-organizing properties of fibroin with elastin resulted in a system that mimicked the extracellular matrix and was able to accelerate wound healing. According to the authors, treatment with a material composed of 50% fibroin and 50% elastin provided the fastest improvement.¹⁵⁸

Enzyme immobilization

Silk fibroin started being used as a support for enzyme immobilization around 1977.²¹² These systems can be easily obtained, not to mention that they increase enzymatic activity and stability.¹⁶¹ Furthermore, silk fibroin can be submitted to different treatments, to optimize enzymatic stabilization through a low-cost material with interesting biological properties.^{163,213,214} Enzymes can be immobilized on fibroin substrates by methods such as covalent bond formation,²¹⁵ adsorption,¹² and encapsulation,^{164–166} among others.¹⁶²

Many enzymes have been immobilized on a fibroin substrate; e.g., HRP (Horseradish peroxidase),²¹⁶ glucose oxidase,²¹⁷ lipase,²¹⁸ and alkaline phosphatase.²¹⁹ In a paper published in 2015, Tao *et al.*²²⁰ used a colorimetric reaction to demonstrate that the HRP activity was maintained after the enzyme was added to the fibroin solution. This led to a functional ink for 3D printing, which would have been impossible to achieve with the enzyme printed in isolation.

Systems comprised of enzymes of interest and fibroin can be used to develop materials for numerous applications in the medical¹⁶² and industrial areas.¹⁶⁵ One example is their use as biosensors for diagnosis.^{14,81}

Electronic and Photonic devices

In the field of electronics and photonics, biopolymer

films have been used to obtain flexible devices.⁷⁵ This field requires materials that can be applied in unconventional interfaces, such as curvy and soft interfaces, to which traditional devices are unable to adhere. Indeed, electrodes that can intimately and non-invasively integrate with these surfaces offer important opportunities for disease treatment and diagnosis.^{16,75} In this regard, fibroin has been extensively studied and stands out against other materials thanks to its unique properties, which include being mechanically robust^{1,14,74} and transparent throughout the visible spectrum, presenting smooth surface and variable refractive index,^{81–83} and being susceptible to physical changes in its structure.^{76,77} All these characteristics allow the preparation of passive or active devices⁷⁵ based on pure fibroin¹⁶ or fibroin in the presence of other components,¹⁶⁷ to provide materials like supports for electrodes,^{16,221} lasers,^{168–174} biosensors,^{175–180} waveguide,^{83,181,182} fuel cells,¹⁸³ and energy storage devices.¹⁸⁴

Kim and collaborators built an electrode consisting of a chip supported on an ultrathin and resorbable fibroin substrate. To this end, they obtained a pure, smooth, and thin film in which the chip was placed. They observed that tissue adhesion improved with decreasing device thickness. The chip could be reabsorbed by the body within a programmed time because fibroin can be undone in days, months, or even years depending on the treatment to which it is submitted.¹⁶ This work introduced a concept that could be extended to other areas: the preparation of electronic devices with biodegradable components as an alternative to replace some types of plastics.

Silva et al.¹⁷² took advantage of the ability of fibroin to copy the characteristics of the substrate to which it is added^{2,14} to prepare a laser system based on the DFB (distributed feedback grating) mechanism by using a commercial DVD as substrate. They poured the fibroin solution on the surface of the DVD and let it dry. The resulting film displayed the diffraction pattern of the DVD. This pattern is what causes amplification in this type of laser system, thus being an example of an active device based on fibroin in the presence of nanoparticles and dye incorporated into the protein structure.¹⁷²

A dielectric material with thickness (l) and refractive index (n_1) and that can support wave propagation is known as a waveguide. Its refractive index (n_1) must be different from the refractive index of the material on which the guide is supported (n_2). In a study published in 2015, researchers obtained biocompatible waveguides from fibroin fiber ($n_1 = 1.54$) encapsulated with fibroin hydrogel ($n_2 = 1.34$) and demonstrated that the materials can guide light in tissues by means of a robust system, thereby allowing great advances in the use of light in therapy or image acquisition.^{83,181}

The fibroin protein structure is also of great interest in the development of photonic devices. Among the amino acids that make up such a structure are the aromatic ami-

no acids tryptophan (Trp), tyrosine (Tyr), and phenylalanine (Phe) (Table 1), which are commonly employed as fluorescent probes for interpretation of the protein structure (conformation, dynamics, and molecular interaction). In the case of fibroin, Trp stands out because its fluorescence is sensitive to the surrounding environment. This amino acid residue, with broadband emission between 300 and 400 nm, can sensitize lanthanide ions by energy transfer, populating the emitter levels more efficiently, as demonstrated in a study published in 2018.⁷⁸ When the emitting levels are more efficiently populated, the emission of these ions intensify, a widely explored phenomenon in photonics.

Understanding how the physicochemical properties of fibroin affect the spectroscopic properties of lanthanide ions can be a strategy for the development of a new generation of photonic devices, such as biocompatible and biodegradable sensors with high transparency in the visible spectral region. In a recently published study, thin, highly transparent films consisting of fibroin and a europium ion (Eu^{3+}) complex, produced by immersion under controlled conditions, were presented. The study showed the highly intense emission typical of Eu^{3+} complexes and the dependence of the intensity of the ${}^5\text{D}_0 \rightarrow {}^7\text{F}_2$ transition on the concentration of ammonia vapor, thus demonstrating the possibility of using this system as a photonic vapor sensor.¹⁸⁰

Final considerations

Silk fibroin has been the focus of several studies on the development of the next technological advancements in the fields of medicine, photonic devices, energy conversion and storage, 3D printing, and electronic devices, for instance. This is because this protein has properties such as mechanical robustness, smooth surface, high transparency ($> 95\%$) throughout the visible region of the spectrum, and high moldability. Therefore, this old and amazing material remains at the cutting-edge of knowledge. Its properties can be improved by further biochemical functionalization, which may provide it with greater versatility for the development of new devices through incorporation of different ions or molecules in the protein structure.

In this way, combining the mechanical and optical properties of fibroin with the multifunctionality of lanthanide ions could be an interesting strategy to develop new, distinguished photonic materials. However, the properties resulting from lanthanides in this protein host have not been fully exploited yet, which opens a wide field for future studies.

Sometimes, fibroin-derived materials do not outperform other inorganic materials. Nevertheless, progress in the synthesis of new composite materials from inorganic particles and fibroin can overcome some drawbacks of pristine fibroin, leading to new materials for solar

cells, 3D print ink, and sensors and to new biomaterials that can be developed on the basis of a green production strategy.

Finally, the silk cocoons that have been produced by the caterpillar *Bombyx mori* for millennia and which have been employed for fabric production had their history changed when their proteins were separated. Fibroin has now become the focus of several research groups and is key for the development of new materials.

Acknowledgment

The authors acknowledge the Brazilian agencies FAPESP (Proc. 2016/11670–5, Proc. 2019/18828–1) and CAPES (23038020092/2016–98) and the University of São Paulo for financial support, and CNPq (141954/2018–3) for the grant received by Roberta Silva Pugina. We thank Cynthia Maria de Campos Prado Manso for careful revision of the text in English.

References

- [1] Omenetto FG and Kaplan DL, New Opportunities for an Ancient Material. *Science* 329 :528–531 (2010).
- [2] Rockwood DN, Preda RC, Yucel T, Wang X, Lovett ML and Kaplan DL, Materials Fabrication from *Bombyx mori* Silk Fibroin. *Nature Protocols* 6 :1612–1631 (2011).
- [3] Pezzolo DB, Tecidos: histórias, tramas, tipos e usos. Senac, São Paulo (2007).
- [4] Kundu B, Rajkhowa R, Kundu SC and Wang X, Silk Fibroin Biomaterials for Tissue Regenerations. *Advanced Drug Delivery Reviews* 4 :457–470 (2013).
- [5] Zaharia C, Tudora MR, Stanescu P, Vasile E and Cincu C, Silk Fibroin Films for Tissue Bioengineering Applications. *Journal of Optoelectronics and Advanced Materials* 14 :163–168 (2012).
- [6] Altman GH, Diaz F, Jakuba C, Calabro T, Horan RL, Chen J, Lu H, Richmond J and Kaplan DL, Silk-based Biomaterials. *Biomaterials* 24 :401–416 (2003).
- [7] Zamboni A, Soares Jr. D, Saldan D, Almeida ED, Círio GM, Oda JY, Pádua OS and Yamaoka RS, Inovações na Sericultura do Paraná: Tecnologias, Manejo e Rentabilidade. Instituto Emater, Londrina (2018).
- [8] Sabbag OJ, Nicodemo D and Oliveira JEM, Custos e Viabilidade Econômica da Produção de Casulos do Bicho-da-seda. *Pesquisa Agropecuária Tropical* 43 :187–194 (2013).
- [9] Fonseca AS and Fonseca TC, Cultura da Amoreira e Criação do Bicho-da-Seda: Sericultura. Nobel, São Paulo (1988).
- [10] Motta A, Fambri L and Migliaresi C, Regenerated Silk Fibroin Films: Thermal and Dynamic Mechanical Analysis. *Macromolecular Chemistry and Physics* 203 :1658–1665 (2002).
- [11] Moy RL, Lee A and Zalka A, Commonly Used Suture Materials in Skin Surgery. *American Family Physician* 44 :2123–2128 (1991).
- [12] Vepari C and Kaplan DL, Silk as a Biomaterial. *Progress in Polymer Science* 32 :991–1007 (2007).
- [13]. Kundu B, Kurland NE, Bano S, Patra C, Engel FB, Yadavalli VK and Kundu SC, Silk Proteins for Biomedical Applications: Bioengineering perspectives. *Progress in Polymer Science* 39 :251–267 (2014).
- [14] Omenetto FG and Kaplan DL, A New Route for Silk. *Nature Photonics* 2 :641–643 (2008).
- [15] Arai T, Freddi G, Innocenti R and Tsukada M, Biodegradation of *Bombyx mori* Silk Fibroin Fibers and Films. *Journal of Applied Polymer Science* 91 :2383–2390 (2004).
- [16] Kim D–H, Viventi J, Amsden JJ, Xiao J, Vigeland L, Kim Y–S, Blanco JA, Panilaitis B, Frechette ES, Contreras D, Kaplan DL, Omenetto FG, Huang Y, Hwang K–C, Zakin MR, Litt B and Rogers JA, Dissolvable Films of Silk Fibroin for Ultrathin Conformal Bio-integrated Electronics. *Nature Materials* 6 :511–517 (2010).
- [17] Strathern P, Confúcio em 90 minutos. Jorge Zahar Ed., Rio de Janeiro (1998).
- [18] Santos VC, de Souza KA, Abrantes RSX, dos Santos CLA, Soares DMA, Loiola MVC, de Lima PMF and dos Santos ELA, Sericultura: Colhendo os Frutos da Criação do Bicho-da-seda. *INTESA- Informativo técnico do semiárido* 10 :62–68 (2016).
- [19] Papavero N and Pujol-Luz JR, Notas Sobre o Bicho-da-seda no Folclore Chinês. *Revista Brasileira de Entomologia* 55 :141 (2011).
- [20] Liu KKC, The Silkworm and Chinese Culture. *Osiris* 10 :129–144 (1952).
- [21] Liu X, The Silk Road in the World History. Oxford, New York (2010).
- [22] Hansen V, The Silk Road. Oxford, New York (2012).
- [23] Gnerre MLA, Rota da Seda: Trânsitos Culturais e Sagrados nos Caminhos da China. *Religare: Revista do Programa de Pós-Graduação em Ciências das Religiões da UFPB* 12 :244–259 (2016).
- [24] Barbosa MP, Lima MC, Fonseca PAA, Júnior RAMG and Alves VL, Nova Rota da Seda e a Ascensão Pacífica Chinesa. *Neari em Revista* 2 :32–51 (2016).
- [25] <https://www.dicionarioinformal.com.br>, access in May

- 2020.
- [26] Regier JC, Mitter C, Zwick A, Bazinet AL, Cummings MP, Kawahara AY, Sohn J-C, Zwickl DJ, Cho S, Davis DR, Baixeras J, Brown J, Parr C, Weller S, Lees DC and Mitter KT, A Large-Scale, Higher-Level, Molecular Phylogenetic Study of the Insect Order Lepidoptera (Moths and Butterflies). *PLOS ONE* 8 :58568 (2013).
- [27] <http://www.usp.br/aunantigo/exibir?id=7780>, access in May 2020.
- [28] Nelson DL, Lehninger – Princípios de Bioquímica. Sarvier, São Paulo (2006).
- [29] dos Santos-Pinto JRA, Arcuri HA, Lubec G and Palma MS, Structural Characterization of the Major Ampullate Silk Spidroin-2 Protein Produced by the Spider *Nephila clavipes*. *Biochimica et Biophysica Acta (BBA)-Proteins and Proteomics* 1864 :1444–1454 (2016).
- [30] Silva LP and Rech EL, Unravelling the biodiversity of nanoscale signatures of spider silk fibres. *Nature Communications* 4 :3014 (2013).
- [31] Bittencourt D, Prosdoci F and Rech EL, Protein Families, Natural History and Biotechnological Aspects of Spider Silk. *Genetics and Molecular Research* 11 :2360–2380 (2012).
- [32] Jin H-J and Kaplan DL, Mechanism of Silk Processing in Insects and Spiders. *Nature* 424 :1057–1061 (2003).
- [33] Ude AU, Eshkoo RA, Zulkifili R, Ariffin AK and Azhari CH, Bombyx Mori Silk Fibre and its Composite: A Review of Contemporary Developments. *Materials and Design* 57 :298–305 (2014).
- [34] Kundu SC, Dash BC, Dash R and Kaplan DL, Natural Protective Glue Protein, Sericin Bioengineered by Silkworms: Potential for Biomedical and Biotechnological Applications. *Progress in Polymer Science* 33 :998–1012 (2008).
- [35] Holanda PRH, da Mata SF and de Lima AGS, Propriedades Físicas e Secagem de Casulos do Bicho-da-Seda em Leito fixo: Uma Investigação Teórica e Experimental. *Revista Brasileira de Produtos Agroindustriais* 6 :101–114 (2004).
- [36] Nicodemo D, de Oliveira JE, Sedano A, Marconcini JM and Tonoli GHD, Impact of Different Silkworm Dietary Supplements on its Silk Performance. *Journal of Materials Science* 49 :6302–6310 (2014).
- [37] <http://www.crisaguil.com/materiales/la-seda.html>, access in May 2020.
- [38] Tao H, Brenckle MA, Yang M, Zhang J, Liu M, Siebert SM, Averitt RD, Mannoor MS, McAlpine MC, Rogers JA, Kaplan DL and Omenetto FG, Silk-based Conformal, Adhesive, Edible Food Sensors. *Advanced Materials* 24 :1067–1072 (2012).
- [39] Marelli B, Brenckle MA, Kaplan DL and Omenetto FG, Silk Fibroin as Edible Coating for Perishable Food Preservation. *Scientific Reports* 6 :25263–255274 (2016).
- [40] Fan JB, Wu LP, Chen LS, Mao XY and Ren FZ, Antioxidant Activities of Silk Sericin From Silkworm *Bombyx Mori*. *Journal of Food Biochemistry* 33 :74–88 (2009).
- [41] Chen X, Knight DP, Shao Z and Vollrath F, Regenerated Bombyx Silk Solutions Studied by Rheometry and FTIR. *Polymer* 42 :9969–9974 (2001).
- [42] Bexiga NM, Bloise AC, de Moraes MA, Converti A, Beppu MM, and Polakiewick B, Production and Characterization of Fibroin Hydrogel Using Waste Silk Fibers. *Fibers and Polymers* 18 :57–63 (2017).
- [43] Nogueira GM, Rodas ACD, Leite CAP, Giles C, Higa OZ, Polakiewick B and Beppu MM, Preparation and Characterization of Ethanol-Treated Silk Fibroin Dense Membranes for Biomaterials Application Using Waste Silk Fibers as Raw Material. *Bioresource Technology* 101 :8446–8451 (2010).
- [44] <https://ocasulofeliz.lojavirtualnuvem.com.br/quem-somos/>, access in May 2020.
- [45] Kujala S, Mannila A, Karvonen L, Kieu K and Sun Z, Natural Silk as a Photonics Component: A Study on Its Light Guiding and Nonlinear Optical Properties. *Scientific Reports* 6 :22358–22367 (2016).
- [46] Tao H, Kaplan DL and Omenetto FG, Silk Materials – A Road to Sustainable High Technology. *Advanced Materials* 24 :2824–2837 (2012).
- [47] Coleman D and Howitt FO, Studies on Silk Proteins; the Properties and Constitution of Fibroin; the Conversion of Fibroin into a Water-Soluble Form and its Bearing on the Phenomenon of Denaturation. *Proceedings of the Royal Society of Medicine* 134 :544 (1947).
- [48] Kon'kov A, Pustovalova O and Agapov I, Biocompatible Materials from Regenerated Silk for Tissue Engineering and Medicinal Therapy. *Applied Biochemistry and Microbiology* 46 :739–744 (2010).
- [49] Zhang Y-Q, Applications of Natural Silk Protein Sericin in Biomaterials. *Biotechnology Advances* 20 :91–100 (2002).
- [50] Kunz RI, Brancalhão RMC, Ribeiro LFC and Natali MRN, Silkworm Sericin: Properties and Biomedical Applications. *BioMed Research International* 1 (2016).
- [51] Sato N, Sato S, Yamanaka A, Yamada H, Fuwa N and Nomura M, Silk Protein, Sericin, Inhibits Lipid Peroxidation and Tyrosinase Activity. *Bioscience, Biotechnology, and Biochemistry* 62 :145–147 (1998).
- [52] Barajas-Gamboa JA, Serpa-Guerra AA, Restrepo-Osorio

- A and Álvarez-López C, Sericin Applications: A Globular Silk Protein. *Ingeniería y Competitividad* 18 :193–206 (2016).
- [53] Padamwar MN, Pawar AP, Daithankar AV and Mahadik KR, Silk Sericin as a Moisturizer: An in vivo Study. *Journal of Cosmetic Dermatology* 4 :250–257 (2005).
- [54] <https://www.youtube.com/watch?v=vqqWw3xkMzA>, access in May 2020.
- [55] Wurn FM, Human Therapeutic Proteins from Silkworms. *Nature Biotechnology* 21 :34–35 (2003).
- [56] Hirabayashi K, Ayub ZH and Kume Y, Gelation of Silk Fibroin. *Transaction* 46 :521–524 (1990).
- [57] Li M, Wu Z, Zhang C, Lu S, Yan H, Huang D and Ye H, Study on Porous Silk Fibroin Materials. II. Preparation and Characteristics of Spongy Porous Silk Fibroin Materials. *Journal of Applied Polymer Science* 79 :2192–2199 (2001).
- [58] Mathur AB, Tonelli A, Rathke T and Hudson S, The Dissolution and Characterization of Bombyx mori Silk Fibroin in Calcium Nitrate-Methanol Solution and the Regeneration of Films. *Biopolymers* 42 :61–74 (1998).
- [59] Khamhaengpol A, Maensiri S and Siri S, Fibroin Protein Extract from Red Ant Nests for a Production of Electrospun Nanofibers. *KKU Research Journal* 15 :919–929 (2010).
- [60] Sun Y, Shao Z, Ma M, Hu P, Liu Y and Yu T, Acrylic Polymer–Silk Fibroin Blend Fibers. *Journal of Applied Polymer Science* 65 :959–966 (1997).
- [61] Tanaka K, Kajiyama N, Ishikura K, Waga S, Kikuchi A, Ohtomo K, Takagi T and Mizuno S, Determination of the Site of Disulfide Linkage Between Heavy and Light Chains of Silk Fibroin Produced by Bombyx mori. *Biochimica et Biophysica Acta* 1432 :92–103 (1999).
- [62] Qi Y, Wang H, Wei K, Yang Y, Zheng R–Y, Kim IS and Zhang K–Q, A Review of Structure Construction of Silk Fibroin Biomaterials from Single Structures to Multi-Level Structures. *International Journal of Molecular Sciences* 18 :237 (2017).
- [63] Tanaka K, Inoue S and Mizuno S, Hydrophobic Interaction of P25, Containing Asn-Linked Oligosaccharide Chains, with the H–L Complex of Silk Fibroin Produced by Bombyx mori. *Insect Biochemistry and Molecular Biology* 29 :269–276 (1999).
- [64] Inoue S, Tanaka K, Arisaka F, Kimura S, Ohtomo K and Mizuno S, Silk Fibroin of Bombyx mori is Secreted, assembling a High Molecular Mass Elementary Unit Consisting of H–chain, L–chain, and P25, with a 6:6:1 Molar Ratio. *Journal of Biological Chemistry* 275 :40517–40528 (2000).
- [65] Marsh RE, Corey RB and Pauling L, An Investigation of the Structure of Silk Fibroin. *Biochimica et Biophysica Acta* 16 :1–34 (1955).
- [66] Valluzzi R, Gido SP, Muller W and Kaplan DL, Orientation of Silk III at the Air–water Interface. *International Journal of Biological Macromolecules* 24 :237–242 (1999).
- [67] Mori K, Tanaka K, Kikuchi T, Waga M, Waga S and Mizuno S, Production of a Chimeric Fibroin Light–chain Polypeptide in a Fibroin Secretion–deficient Naked Pupa Mutant of the Silkworm Bombyx mori. *Journal of Molecular Biology* 25 :217–228 (1995).
- [68] Zhou CZ, Confalonieri F, Jacquet M, Perasso R, Li Z–G and Janin J, Silk Fibroin: Structural Implications of a Remarkable Amino Acid Sequence. *PROTEINS: Structure, Function, and Genetics* 44 :119–122 (2001).
- [69] Volkov V and Cavaco–Paulo A, In Vitro Phosphorylation as Tool for Modification of Silk and Keratin Fibrous Materials. *Applied Microbiology and Biotechnology* 100 :4337–4345 (2016).
- [70] Drummy LF, Phillips DM, Stone MO and Naik RR, Thermally Induced α –Helix to β –Sheet Transition in Regenerated Silk Fibers and Films. *Biomacromolecules* 6 :3328–3333 (2005).
- [71] Numata K, Cebe P and Kaplan DL, Mechanism of Enzymatic Degradation of Beta–sheet Crystals. *Biomaterials* 10 :2926–2933 (2010).
- [72] Yang Y, Shao Z, Chen X and Zhou P, Optical Spectroscopy To Investigate the Structure of Regenerated Bombyx mori Silk Fibroin in Solution. *Biomacromolecules* 5 :773–779 (2004).
- [73] Meng Z, Zheng X, Tang K, Liu J and Qin S, Dissolution of Natural Polymers in Ionic Liquids: A Review. *E–Polymers* 28 :1–29 (2012).
- [74] Jiang C, Wang X, Gunawidjaja R, Lin Y–H, Gupta MK, Kaplan DL, Naik RR and Tsukruk VV, Mechanical Properties of Robust Ultrathin Silk Fibroin Films. *Advanced Functional Materials* 17 :2229–2237 (2007).
- [75] Zhu B, Wang H, Leow WR, Cai Y, Loh XJ, Han M–Y and Chen X, Silk Fibroin for Flexible Electronic Devices. *Advanced Materials* 28 :4250–4265 (2015).
- [76] Koh L–D, Cheng Y, Teng C–P, Khin Y–W, Loh X–J, Tee S–Y, Low M, Ye E, Yu H–D, Zhang Y–Z and Han M–Y, Structures, Mechanical Properties and Applications of Silk Fibroin Materials. *Progress in Polymer Science* 46 :86–110 (2015).
- [77] Jimenez DEQ, Ferreira IM, Yoshioka SA and Fonseca LP, Silk Fibroin Functionalized with CuSO₄ on Knoevenagel Condensation Under Microwave Radiation. *Current Microwave Chemistry* 4 :131–138 (2017).

- [78] Pugina RS, da Rocha EG, Ribeiro SJL and Caiut JMA, Study of the Energy Transfer Process in Rare Earth-doped Silk Fibroin for Future Application in Luminescent Compounds. *Journal of Luminescence* 205 :423–428 (2019).
- [79] Pugina RS, da Rocha EG and Caiut JMA, Beta-diketones in the Intensification of the Luminescence of the Silk Fibroin Films Doped Rare Earth Ions. *Journal of Materials Science: Materials in Electronics* 30 :16732–16739 (2019).
- [80] Minoura N, Tsukada M and Nagura M, Physico-chemical Properties of Silk Fibroin Membrane as a Biomaterial. *Biomaterials* 11 :430–434 (1990).
- [81] Lawrence BD, Golomb MC, Georgakoudi I, Kaplan DL and Omenetto FG, Bioactive Silk Protein Biomaterial Systems for Optical Devices. *Biomacromolecules* 9 :1214–1220 (2008).
- [82] Okamoto K, *Fundamentals of Optical Waveguides*. Academic Press, Cambridge (2005).
- [83] Applegate MB, Perotto G, Kaplan DL and Omenetto FG, Biocompatible Silk Step-index Optical Waveguides. *Bio-medical Optics Express* 6 :4221–4227 (2015).
- [84] Sacco BL and de Santana H, Impact of Temperature on the Stability of Silkworm Cocoon Fibers. *Química Nova* 42 :1014–1019 (2019).
- [85] Kawahara Y, Furukawa K and Yamamoto T, Self-Expansion Behavior of Silk Fibroin Film. *Macromolecular Materials and Engineering* 291 :458–462 (2006).
- [86] Nogueira GM, Swiston AJ, Beppu MM and Rubner MF, Layer-by-layer Deposited Chitosan/silk Fibroin Thin Films with Anisotropic Nanofiber Alignment. *Langmuir* 26 :8953–8958 (2010).
- [87] Pereira RFP, Silva MM and Bermudez VZ, Bombyx mori Silk Fibers: An Outstanding Family of Materials. *Macromolecular Materials and Engineering* 300 :1171–1198 (2014).
- [88] Jin H-J, Karageorgiou V, Kim U-J, Valluzzi R, Cebe P and Kaplan DL, Water Stable Silk Films with Reduced β -Sheet Content. *Advanced Functional Materials* 15 :1241–1247 (2005).
- [89] Lawrence BD, Wharram S, Kluge JA, Leisk GG, Omenetto FG, Rosenblatt MI and Kaplan DL, Effect of Hydration on Silk Film Material Properties. *Macromolecular Bioscience* 10 :393–403 (2010).
- [90] Hu X, Shmelev K, Sun L, Gil E-S, Park S-H, Cebe P and Kaplan DL, Regulation of Silk Material Structure by Temperature-controlled Water Vapor Annealing. *Biomacromolecules* 12 :1686–1696 (2011).
- [91] Freddi G, Tsukada M and Beretta S, Structure and Physical Properties of Silk Fibroin/Polyacrylamide Blend Films. *Journal of Applied Polymer Science* 71 :1563–1571 (1999).
- [92] Lopes LM, de Moraes MA and Beppu MM, Study of Phase Separation in Blends of Silk Fibroin and Sodium Alginate in Solution and in Solid State. *Journal of Polymer Research* 25 :198 (2018).
- [93] de Moraes MA and Beppu MM, Biocomposite Membranes of Sodium Alginate and Silk Fibroin Fibers for Biomedical Applications. *Journal of Applied Polymer Science* 130 :3451–3457 (2013).
- [94] Silva MF, de Moraes MA, Nogueira GM, Rodas ACD, Higa OZ and Beppu MM, Glycerin and Ethanol as Additives on Silk Fibroin Films: Insoluble and Malleable Films. *Journal of Applied Polymer Science* 128 :115–122 (2012).
- [95] Bittencourt PRS, de Souza LM, Zanotelli N and Scremin FR, Incorporation of Fibroin from Bombyx Mori and Nanotubes in Polyamide 6 Systems. *Acta Brasiliensis* 2 :106–108 (2018).
- [96] França CG, Nascimento VF, Hernandez-Montelongo J, Machado D, Lancellotti M and Beppu MM, Synthesis and Properties of Silk Fibroin/Konjac Glucomannan Blend Beads. *Polymers* 10 :923 (2018).
- [97] Ghaeli I, de Moraes MA, Beppu MM, Lewandowska K, Sionkowska A, da Silva FF, Ferraz MP and Monteiro FJ, Phase Behaviour and Miscibility Studies of Collagen/Silk Fibroin Macromolecular System in Dilute Solutions and Solid State. *Molecules* 22 :1368 (2017).
- [98] de Moraes MA, Silva MF, Weska RF and Beppu MM, Silk Fibroin and Sodium Alginate Blend: Miscibility and Physical Characteristics. *Materials Science and Engineering: C- Materials for Biological Applications* 40 :85 (2014).
- [99] de Moraes MA, Nogueira GM, Weska RF and Beppu MM, Preparation and Characterization of Insoluble Silk Fibroin/Chitosan Blend Films. *Polymers* 2 :719–727 (2010).
- [100] Karp JR, Hamerski F, Silva VR, Supported Silk Fibroin/Poly(Vinyl Alcohol) Membrane Blends: Structure, Properties, and Ethanol Dehydration by Pervaporation. *Polymer Engineering and Science* 58 :1879–1887 (2017).
- [101] Jin H-J, Park J, Valluzzi R, Cebe P and Kaplan DL, Biomaterial Films of Bombyx Mori Silk Fibroin with Poly(ethylene oxide). *Biomacromolecules* 5 :711–717 (2004).
- [102] Lovett ML, Cannizzaro CM, Vunjak-Novakovic G and Kaplan DL, Gel Spinning of Silk Tubes for Tissue Engineering. *Biomaterials* 29 :4650–4657 (2008).
- [103] Weska RF, Vieira Jr. WC, Nogueira GM and Beppu MM, Effect of Freezing Methods on the Properties of Lyophilized Porous Silk Fibroin Membranes. *Materials Research* 12 :233–237 (2009).
- [104] Ramirez SMV, de Moraes MA and Beppu MM, Assessing The Influence of Silkworm Cocoon's Age on the Physi-

- cochemical Properties of Silk Fibroin-Based Materials. *Journal of Materials Research* 34 :1944–1949 (2019).
- [105] Kweon HK, Kang S-W, Lee K-G, Park KY, Jo YY, Kang P-D, Sung G-N, Lee HS, Yeo J-H, Shin K-H and Park C-H, Solubility and Conformation of Silk Fibroin Membrane. *International Journal of Industrial Entomology* 22 :101–105 (2011).
- [106] Moraes ML, Lima LR, Silva RR, Cavicchioli M and Ribeiro SJL, Immunosensor Based on Immobilization of Antigenic Peptide NS5A-1 from HCV and Silk Fibroin in Nanostructured Films. *Langmuir* 29 :3829–3834 (2013).
- [107] Cai K, Hu Y and Jandt KD, Surface Engineering of Titanium Thin Films with Silk Fibroin via Layer-by-Layer Technique and its Effects on Osteoblast Growth Behavior. *Journal of Biomedical Materials Research* 82A :927–935 (2007).
- [108] de Moraes MA, Crouzier T, Rubner MF and Beppu MM, Factors Controlling the Deposition of Silk Fibroin Nano-Fibrils During Layer-by-Layer Assembly. *Biomacromolecules* 16 :97–104 (2015).
- [109] Perry H, Gopinath A, Kaplan DL, Negro LD and Omenetto FG, Nano and Micropatterning of Optically Transparent, Mechanically Robust, Biocompatible Silk Fibroin Films. *Advanced Materials* 20 :3070–3072 (2008).
- [110] Terada D, Yokoyama Y, Hattori S, Kobayashi H and Tamada Y, The Outermost Surface Properties of Silk Fibroin Films Reflect Ethanol-Treatment Conditions Used in Biomaterial Preparation. *Materials Science and Engineering: C- Materials for Biological Applications* 58 :119–126 (2016).
- [111] Muller WS, Samuelson LA, Fossey SA and Kaplan DL, Formation and Characterization of Langmuir Silk Films. *Langmuir* 9 :1857–1861 (1993).
- [112] Higuchi A, Yoshida M, Ohno T, Asakura T and Hara M, Production of Interferon- β in A Culture of Fibroblast Cells on Some Polymeric Films. *Cytotechnology* 34 :165–173 (2000).
- [113] Lovett M, Cannizzaro C, Daheron L, Messmer B, Vunjak-Novakovic G and Kaplan DL, Silk Fibroin Microtubes for Blood Vessel Engineering. *Biomaterials* 28 :5271–5279 (2007).
- [114] Wenk E, Wandrey AJ, Merkle HP and Meinel L, Silk Fibroin Spheres as a Platform for Controlled Drug Delivery. *Journal of Controlled Release* 132 :26–34 (2008).
- [115] Wang X, Wenk E, Matsumoto A, Meinel L, Li C and Kaplan DL, Silk Microspheres for Encapsulation and Controlled Release. *Journal of Controlled Release* 117 :360–370 (2007).
- [116] Wang X, Yucel T, Lu Q, Xu X and Kaplan DL, Silk Nanospheres and Microspheres from Silk/Pva Blend Films for Drug Delivery. *Biomaterials* 31 :1025–1035 (2010).
- [117] Kim SH, Nam YS, Lee TS and Park WH, Silk Fibroin Nanofiber. *Electrospinning, Properties, and Structure. Polymer Journal* 35 :185–190 (2003).
- [118] Müller V, Cestari M, Palácio SM, de Campos SD, Muniz EC and de Campos EA, Silk Fibroin Nanofibers Electrospun on Glass Fiber as a Potential Device for Solid Phase Microextraction. *Journal of Applied Polymer Science* 132 :41717 (2014).
- [119] Jin H-J, Fridrikh SV, Rutledge GC and Kaplan DL, Electrospinning Bombyx mori Silk with Poly(ethylene oxide). *Biomacromolecules* 3 :1233–1239 (2002).
- [120] Li C, Vepari C, Jin HJ, Kim HJ and Kaplan DL, Electrospun Silk-BMP-2 Scaffolds for Bone Tissue Engineering. *Biomaterials* 27 :3115–3124 (2006).
- [121] Rapanas A, Andriopoulou S and Glasmacher B, The Significance of Electrospinning as a Method to Create Fibrous Scaffolds for Biomedical Engineering and Drug Delivery Applications. *Journal of Drug Delivery Science and Technology* 31 :137–146 (2016).
- [122] Peng Q, Shao H, Hu X and Zhang Y, Microfluidic Dry-spinning and Characterization of Regenerated Silk Fibroin Fibers. *Journal of Visualized Experiments* 127 :56271 (2017).
- [123] Kim U-J, Park J, Kim HJ, Wada M and Kaplan DL, Three-Dimensional Aqueous-Derived Biomaterial Scaffolds from Silk Fibroin. *Biomaterials* 26 :2775–2785 (2005).
- [124] Nazarov R, Jin H-J and Kaplan DL, Porous 3-D Scaffolds from Regenerated Silk Fibroin. *Biomacromolecules* 5 :718–726 (2004).
- [125] Yucel T, Kojic N, Leisk GG, Lo TJ and Kaplan DL, Non-Equilibrium Silk Fibroin Adhesives. *Journal of Structural Biology* 170 :406–412 (2010).
- [126] Wang X, Kluge JA, Leisk GG and Kaplan DL, Sonication-Induced Gelation of Silk Fibroin for Cell Encapsulation. *Biomaterials* 29 :1054–1064 (2008).
- [127] Leisk GG, Lo TJ, Yucel T, Lu Q and Kaplan DL, Electrogelation for Protein Adhesives. *Advanced Materials* 22 :711–715 (2010).
- [128] Nogueira GM, de Moraes MA, Rodas ACD, Higa OZ and Beppu MM, Hydrogels from Silk Fibroin Metastable Solution: Formation and Characterization from a Biomaterial Perspective. *Materials Science and Engineering C* 31 :997–1001 (2011).
- [129] Montalban MG, Chakraborty S, Peña-García J, Verli H, Villora G, Pérez-Sánchez H and Díaz-Baños G, Molecular Insight into Silk Fibroin Based Delivery Vehicle for Amphiphilic Drugs: Synthesis, Characterization and Molecular Dynamics Studies. *Journal of Molecular Liquids* 299 :112156 (2020).
- [130] Tomoda BT, Corazza FG, Beppu MM, Lopes PS and de Moraes MA, Silk Fibroin Membranes with Self-Assembled Globular Structures for Controlled Drug Release. *Journal of Applied Polymer Science* 137 :48763 (2020).

- [131] Nascimento TRL, Velo MMAC, Silva CF, Cruz SBSC, Gondim BLC, Mondelli RFL and Castellano LRC, Current Applications of Biopolymer-based Scaffolds and Nanofibers as Drug Delivery Systems. *Current Pharmaceutical Design* 25 :3997–4012 (2019).
- [132] de Moraes MA, Mahl CRA, Silva MF and Beppu MM, Formation of Silk Fibroin Hydrogel and Evaluation of its Drug Release Profile. *Journal of Applied Polymer Science* 132 :41802 (2015).
- [133] Wenk E, Merkle HP and Meinel L, Silk Fibroin as a Vehicle for Drug Delivery Applications. *Journal of Controlled Release* 150 :128–141 (2011).
- [134] Hofmann S, Wong Po Foo CT, Rossetti FF, Textor M, Vunjak–Novakovic G, Kaplan DL, Merkle HP and Meinel L, Silk Fibroin as an Organic Polymer for Controlled Drug Delivery. *Journal of Controlled Release* 111 :219–227 (2006).
- [135] Pritchard LM and Kaplan DL, Silk Fibroin Biomaterials for Controlled Release Drug Delivery. *Expert Opinion on Drug Delivery* 8 :797 (2011).
- [136] Long K, Liu Y, Li W, Wang L, Liu S, Wang Y, Wang Z and Ren L, Improving the Mechanical Properties of Collagen Based Membranes Using Silk Fibroin for Corneal Tissue Engineering. *Journal of Biomedical Materials Research A* 103 :1159–1168 (2014).
- [137] Harkin DG, George KA, Madden PW, Schwab IR, Huttmacher DW and Chirila TV, Silk Fibroin in Ocular Tissue Reconstruction. *Biomaterials* 32 2445–2458 (2011).
- [138] Liu J, Lawrence BD, Liu A, Schwab IR, Oliveira LA and Rosenblatt MI, Silk Fibroin as a Biomaterial Substrate for Corneal Epithelial Cell Sheet Generation. *Investigative Ophthalmology & Visual Science* 53 :4130–4138 (2012).
- [139] Cubayachi C, Lemos CN, Pereira F, Dias K, Herculano RD, de Freitas O and Lopez RFV, Silk Fibroin Films Stabilizes and Releases Bioactive Insulin for the Treatment of Corneal Wounds. *European Polymer Journal* 118 :502–513 (2019).
- [140] Wang S, Ghezzi CE, Gomes R, Pollard RE, Funderburgh JL and Kaplan DL, In Vitro 3D Corneal Tissue Model with Epithelium, Stroma, and Innervation. *Biomaterials* 112 :1–9 (2017).
- [141] Tu F, Li Y, Li H, Shi P, Hao Y, Wu Y, Yi H, Yin Y and Wang J, Vascular Cell Co–Culture on Silk Fibroin Matrix Polymer 10 :39 (2018).
- [142] Liu H, Li X, Zhou G, Fan H and Fan Y, Electrospun Sulfated Silk Fibroin Nanofibrous Scaffolds for Vascular Tissue Engineering. *Biomaterials* 32 :3784–3793 (2011).
- [143] de Moraes MA, Paternotte E, Mantovani D and Beppu MM, Mechanical and Biological Performances of New Scaffolds Made of Collagen Hydrogels and Fibroin Microfibers for Vascular Tissue Engineering. *Macromolecular Bioscience* 12 :1253–1264 (2012).
- [144] Paternotte E, de Moraes MA, Beppu MM and Mantovani D, Collagen–Silk Fibroin Fibers: A Promising Scaffold for Vascular Tissue Engineering. *Materials Science Forum* 706 :572–577 (2012).
- [145] Coelho F, Cavicchioli M, Specian SS, Cilli EM, Ribeiro SJL, Scarel–Caminaga RM and Capote TSO, Silk Fibroin/Hydroxyapatite Composite Membranes: Production, Characterization and Toxicity Evaluation. *Toxicology in Vitro* 62 :104670 (2020).
- [146] Lopes JH, França CG and Beppu MM, Development and Characterization of Membranes Derived from SF/GLY/58S Hybrid Xerogels for the Release of Inorganic Ions as an Osteogenic Stimulus for Bone Regeneration. *European Polymer Journal* 116 :425–437 (2019).
- [147] Ribeiro M, Fernandes MH, Beppu MM, Monteiro FJ and Ferraz MP, Silk Fibroin/Nanohydroxyapatite Hydrogels for Promoted Bioactivity and Osteoblastic Proliferation and Differentiation of Human Bone Marrow Stromal Cells. *Materials Science and Engineering: C* 89 :336–345 (2018).
- [148] Ribeiro M, Ferraz MP, Monteiro FJ, Fernandes MH, Beppu MM, Mantione D and Sardon H, Antibacterial Silk Fibroin/Nanohydroxyapatite Hydrogels with Silver and Gold Nanoparticles for Bone Regeneration. *Nanomedicine* 13 :231–239 (2017).
- [149] Ribeiro M, de Moraes MA, Beppu MM, Garcia MP, Fernandes MH, Monteiro FJ and Ferraz MP, Development of Silk Fibroin/Nanohydroxyapatite Composite Hydrogels for Bone Tissue Engineering. *European Polymer Journal* 67 :66–77 (2015).
- [150] Lima PAL, Resende CX, Soares GDA, Anselme K and Almeida LE, Preparation, Characterization and Biological Test of 3D–Scaffolds Based on Chitosan, Fibroin and Hydroxyapatite for Bone Tissue Engineering. *Materials Science and Engineering: C* 33 :3389–3395 (2013).
- [151] Weska RF, Nogueira GM, Vieira WC and Beppu MM, Porous Silk Fibroin Membrane as a Potential Scaffold for Bone Regeneration. *Key Engineering Materials* 396 :187–190 (2009).
- [152] Jin H–J, Chen J, Karageorgiou V, Altman GH and Kaplan DL, Human Bone Marrow Stromal Cell Responses on Electrospun Silk Fibroin Mats. *Biomaterials* 25 :1039–1047 (2004).
- [153] Melke J, Midha S, Ghosh S, Ito K and Hofmann S, Silk Fibroin as Biomaterial for Bone Tissue Engineering. *Acta Biomaterials* 31 :1–16 (2016).
- [154] Sommer MR, Vetsch JR, Leemann J, Müller R, Studart AR and Hofmann S, Silk Fibroin Scaffolds with Inverse Opal Structure for Bone Tissue Engineering. *Journal of Biomedical Materials Research* 105 :2074–2084 (2016).
- [155] Gu Z, Xie H, Li L and Yu X, Preparation of Chitosan/Silk Fibroin Blending Membrane Fixed with Alginate Dialdehyde for Wound Dressing. *International Journal of Biological Macromolecules* 58 :121–126 (2013).
- [156] Pacheco MS, Kano GE, Paulo LA, Lopes PS and de Moraes

- MA, Silk Fibroin/Chitosan/Alginate Multilayer Membranes as a System for Controlled Drug Release in Wound Healing. *International Journal of Biological Macromolecules* 152 :803–811 (2020).
- [157] Lemos CN, Cubayachi C, Dias K, Mendonça JN, Lopes NP, Furtado NAJC and Lopez RFV, Iontophoresis–Stimulated Silk Fibroin Films as a Peptide Delivery System for Wound Healing. *European Journal of Pharmaceutics and Biopharmaceutics* 128 :147–155 (2018).
- [158] Vasconcelos A, Gomes AC and Cavaco–Paulo A, Novel Silk Fibroin/Elastin Wound Dressings. *Acta Biomaterials* 8 :3049–3060 (2012).
- [159] Yan L–P, Silva–Correia J, Ribeiro VP, Miranda–Gonçalves V, Correia C, Morais AS, Sousa RA, Reis RM, Oliveira AL, Oliveira JM and Reis RL, Tumor Growth Suppression Induced by Biomimetic Silk Fibroin Hydrogels. *Science Report* 6 :31037 (2016).
- [160] Rojas JEU, Gerbelli BB, Ribeiro AO, Nantes–Cardoso IL, Giuntini F and Alves WA, Silk Fibroin Hydrogels for Potential Applications in Photodynamic Therapy. *Biopolymer* 110 :e23245 (2019).
- [161] Zhang Y–Q, Natural Silk Fibroin as a Support for Enzyme Immobilization. *Biotechnology Advances* 16 :961–971 (1998).
- [162] Pritchard EM, Dennis PB, Omenetto FG, Naik RR and Kaplan DL, Physical and Chemical Aspects of Stabilization of Compounds in Silk. *Biopolymers* 97 :479–498 (2012).
- [163] Bezerra CS, Lemos CMGF, de Sousa M and Gonçalves LRB, Enzyme Immobilization onto Renewable Polymeric Matrixes: Past, Present, and Future Trends. *Journal of Applied Polymer Science* 132 :42125 (2015).
- [164] Ferreira IM, Yoshioka SA, Comasseto JV and Porto ALM, Immobilization of Amano Lipase from *Pseudomonas Fluorescens* on Silk Fibroin Spheres: an Alternative Protocol for the Enantioselective Synthesis of Halohydrins. *RSC Advanced* 7 :12650–12658 (2017).
- [165] Ferreira IM, Ganzeli1 LS, Rosset IG, Yoshioka SA and Porto ALM, Ethylic Biodiesel Production Using Lipase Immobilized in Silk Fibroin–Alginate Spheres by Encapsulation. *Catalysis Letters* 147 :268–280 (2017).
- [166] Ferreira IM, Nishimura RHV, Souza ABA, Clososki GC, Yoshioka SA and Porto ALM, Highly Enantioselective Acylation of Chlorohydrins Using Amano AK Lipase from *P. Fluorescens* Immobilized on Silk Fibroin–Alginate Spheres. *Tetrahedron Letters* 55 :5062–5065 (2014).
- [167] da Silva RR, Cavicchioli M, Lima LR, Otoni CG, Barud HS, Santagneli SH, Tercjak A, Amaral AC, Carvalho RA and Ribeiro SJL, Fabrication of Biocompatible, Functional, and Transparent Hybrid Films Based on Silk Fibroin and Epoxy Silane for Biophotonics. *ACS Applied Materials & Interfaces* 9 :27905–27917 (2017).
- [168] Paula KT, Santos MV, Facure MHM, Andrade MB, Araújo FL, Correa DS, Ribeiro SJL and Mendonça CR, Laser Patterning and Induced Reduction of Graphene Oxide Functionalized Silk Fibroin. *Optical Materials* 99 :109540 (2020).
- [169] Santos MV, Santos SNC, Martins RJ, Almeida JMP, Paula KT, Almeida GFB, Ribeiro SJL and Mendonça CR, Femtosecond Direct Laser Writing of Silk Fibroin Optical Waveguides. *Journal of Materials Science: Materials in Electronics* 30 :16843–16848 (2019).
- [170] Soares JMD, Menezes LS, Pincheira PIR, Rojas–Ulloa C, Gomez NR, de Oliveira H and Gomes ASL, Plasmonically Enhanced Hybrid Metalorganic Random Laser in Eggshell Biomembrane. *Optical Materials* 91 :205–211 (2019).
- [171] Santos MV, Pecoraro E, Santagneli SH, Moura AL, Cavicchioli M, Jerez V, Rocha LA, de Oliveira LFC, Gomes ASL, de Araújo CB and Ribeiro SJL, Silk Fibroin as a Biotemplate for Hierarchical Porous Silica Monoliths for Random Laser Applications. *Journal of Materials Chemistry C* 6 :2712 (2018).
- [172] da Silva RR, Dominguez CT, dos Santos MV, Barbosa–Silva R, Cavicchioli M, Christovan LM, de Melo LSA, Gomes ASL, de Araújo CB and Ribeiro SJL, Silk Fibroin Biopolymer Films as Efficient Hosts for DFB Laser Operation. *Journal of Materials Chemistry C* 43 :7181 (2013).
- [173] Toffanin S, Kim S, Cavallini S, Natali M, Benfenati V, Amsden JJ, Kaplan DL, Zamboni R, Muccini M and Omenetto FG, Low–Threshold Blue Lasing from Silk Fibroin Thin Films. *Applied Physics Letters* 101 :091110 (2012).
- [174] Maximova K, Wang X, Balčytis A, Fan L, Li J and Juodkasis S, Silk Patterns Made by Direct Femtosecond Laser Writing. *Biomicrofluidics* 10 :054101 (2016).
- [175] Moraes MM, Lima LR, Vicentini–Oliveira J, de Souza AV, Oliveira O, Deffune E and Ribeiro SJL, Immunosensor for the Diagnostics of Autoimmune Hemolytic Anemia (AIHA) Based on Immobilization of a Monoclonal Antibody on a Layer of Silk Fibroin. *Journal of Nanoscience and Nanotechnology* 19 :3772–3776 (2019).
- [176] Lima LR, Gonçalves AB, Paulovich FV, Oliveira Jr. ON, Ribeiro SJL and Moraes ML, Electrical Immunosensor Made with Antigenic Peptide NS5A–1 Immobilized onto Silk Fibroin for Diagnosing Hepatitis C. *Journal of the Brazilian Chemical Society* 29 :2054 (2018).
- [177] Delezuk JAM, Pavinatto A, Moraes ML, Shimizu FM, Rodrigues VC, Campana–Filho SP, Ribeiro SJL and Oliveira Jr. ON, Silk Fibroin Organization Induced by Chitosan in Layer–By–Layer Films: Application as a Matrix in a Biosensor. *Carbohydrate Polymers* 155 :146–151 (2017).
- [178] Gonçalves JM, Lima LR, Moraes ML and Ribeiro SJL, Immunosensor for Diagnosis of Alzheimer Disease Using Amyloid–B 1–40 Peptide and Silk Fibroin Thin Films. *Materials Science and Engineering: C* 68 :338–342 (2016).
- [179] Lima LR, Moraes ML, Nigoghossian K, Peres MFS and Ribeiro SJL, Silk Fibroin–Antigenic Peptides–YVO₄:Eu³⁺ Nanostructured Thin Films as Sensors for Hepatitis C. *Journal of Luminescence* 170 :375–379 (2016).

- [180] da Rocha EG, Pugina RS and Caiut JMA, Luminescent Sensor Based on the Lanthanide–Fibroin Composite. *Optical Materials* 109 :110236 (2020).
- [181] Parker ST, Domachuk P, Amsden J, Bressner J, Lewis JA, Kaplan DL and Omenetto FG, Biocompatible Silk Printed Optical Waveguides. *Advanced Materials* 21 :2411–2415 (2009).
- [182] Prajzler V, Min K, Kim S and Nekvindova P, The Investigation of the Waveguiding Properties of Silk Fibroin from the Visible to Near–Infrared Spectrum. *Materials* 11 :112 (2018).
- [183] Pasternaka G, Yang Y, Santos BB, Brunello F, Hanczyc MM and Motta A, Regenerated Silk Fibroin Membranes as Separators for Transparent Microbial Fuel Cells. *Bioelectrochemistry* 126 :146–155 (2019).
- [184] Jia X, Wang C, Ranganathan V, Napier B, Yu C, Chao Y, Forsyth M, Omenetto FG, MacFarlane DR and Wallace GG, A Biodegradable Thin–Film Magnesium Primary Battery Using Silk Fibroin–Ionic Liquid Polymer Electrolyte. *ACS Energy Letter* 2 :831–836 (2017).
- [185] Park WH, Ha WS, Ito H, Miyamoto T, Inagak H, Noishiki Y, Relationships Between Antithrombogenicity and Surface Free Energy of Regenerated Silk Fibroin Films. *Fibers and Polymers* 2 :58–63 (2001).
- [186] Zamani M, Khafaji M, Naji M, Vossoughi M, Alemzadeh I and Haghighipour N, A Biomimetic Heparinized Composite Silk–Based Vascular Scaffold with sustained Antithrombogenicity. *Scientific Reports* 7 :4455 (2017).
- [187] Langer R, Polymeric Delivery Systems for Controlled–Drug Release. *Chemical Engineering Communications* 6 :1–48 (1980).
- [188] Chien Y, *Novel Drug Delivery Systems*. CRC Press, Boca Raton (1991).
- [189] Kasoju N and Bora U, Silk Fibroin in Tissue Engineering. *Advanced Healthcare Materials* 1 :393–412 (2012).
- [190] Ghosh S, Parker ST, Wang X, Kaplan DL and Lewis JA, Direct–Write Assembly of Microperiodic Silk Fibroin Scaffolds for Tissue Engineering Applications. *Advanced Functional Materials* 18 :1883–1889 (2008).
- [191] Li ZH, Ji SC, Wang YZ, Shen XC and Liang H, Silk Fibroin–Based Scaffolds for Tissue Engineering. *Frontiers of Materials Science* 7 :237–247 (2013).
- [192] Lara–Cerón JA, Jiménez–Pérez VM, Molina–Paredes AA, Ochoa ME, Sábio RM, Amaral AC, da Silva RR, Ribeiro SJL, Barud HS and Muñoz–Flores BM, Ultrasound–Assisted Synthesis of Organotin Compounds and Their Application as Luminescent Dye in Silk Fibroin Scaffolds. *Inorganica Chimica Acta* 505 :119490 (2020).
- [193] Magaz A, Roberts AD, Faraji S, Nascimento TRL, Medeiros ES, Zhang W, Greenhalgh RD, Mautner A, Li X and Blaker JJ, Porous, Aligned, and Biomimetic Fibers of Regenerated Silk Fibroin Produced by Solution Blow Spinning. *Bio–macromolecules* 19 :4543–4553 (2018).
- [194] Barud HGO, Barud HS, Cavicchioli M, Amaral TS, de Oliveira Jr. OB, Santos DM, Petersen ALOA, Celes F, Borges VM, de Oliveira CI, de Oliveira PF, Furtado RA, Tavares DC and Ribeiro SJL, Preparation and Characterization of a Bacterial Cellulose/Silk Fibroin Sponge Scaffold for Tissue Regeneration. *Carbohydrate Polymers* 128 :41–51 (2015).
- [195] Cestari M, Muller V, Rodrigues JHS, Nakamura CV, Rubira AF, Muniz EC, Preparing Silk Fibroin Nanofibers Through Electrospinning: Further Heparin Immobilization Toward Hemocompatibility Improvement. *Biomacromolecules* 15 :1762–1767 (2014).
- [196] Nogueira GM, Weska RF, Vieira Jr. WC, Polakiewicz B, Rodas ACD, Higa OZ and Beppu MM, A New Method to Prepare Porous Silk Fibroin Membranes Suitable for Tissue Scaffolding Applications. *Journal of Applied Polymer Science* 114 :617–623 (2009).
- [197] Chen CH, Liu JM, Chua CK, Chou SM, Shyu VB and Chen JP, Cartilage Tissue Engineering with Silk Fibroin Scaffolds Fabricated by Indirect Additive Manufacturing Technology. *Materials* 7 :2104–2119 (2014).
- [198] Talukdara S, Nguyenb QT, Chen AC, Sah RL and Kundu SC, Effect of Initial Cell Seeding Density on 3D–Engineered Silk Fibroin Scaffolds for Articular Cartilage Tissue Engineering. *Biomaterials* 32 :8927–8937 (2011).
- [199] Foss C, Merzari E, Migliaresi C and Motta A, Silk Fibroin/Hyaluronic Acid 3D Matrices for Cartilage Tissue Engineering. *Biomacromolecules* 14 :38–47 (2013).
- [200] Wang Y, Blasioli DJ, Kim HJ, Kim HS and Kaplan DL, Cartilage Tissue Engineering with Silk Scaffolds and Human Articular Chondrocytes. *Biomaterials* 27 :4434–4442 (2006).
- [201] Bhardwaja N, Nguyenb QT, Chen AC, Kaplan DL, Sah RL and Kundu SC, Potential of 3–D Tissue Constructs Engineered from Bovine Chondrocytes/Silk Fibroin–Chitosan for in Vitro Cartilage Tissue Engineering. *Biomaterials* 32 :5773–5781 (2011).
- [202] Aoki H, Tomita N, Morita Y, Hattori K, Harada Y, Sonobe M, Wakitani S and Tamada Y, Culture of Chondrocytes in Fibroin–Hydrogel Sponge. *Bio–Medical Materials and Engineering* 13 :309–316 (2003).
- [203] Silva SS, Motta A, Rodrigues MT, Pinheiro AFM, Gomes ME, Mano JF, Reis RL and Migliaresi C, Novel Genipin–Cross–Linked Chitosan/Silk Fibroin Sponges for Cartilage Engineering Strategies. *Biomacromolecules* 9 :2764–2774 (2008).
- [204] Minoura N, Aba S–I, Gotoh Y, Tsukada M and Imai Y, Attachment and Growth of Fibroblast Cells on Silk Fibroin. *Biochemical and Biophysical Research Communications* 208 :511–516 (1995).
- [205] Sofia S, McCarthy MB, Gronowicz G and Kaplan DL, Functionalized Silk–Based Biomaterials for Bone Formation. *Journal of Biomedical Materials Research* 54 :139–148 (2001).

- [206] Chen J, Altman GH, Karageorgiou V, Horan R, Collette A, Volloch V, Colabro T and Kaplan DL, Human Bone Marrow Stromal Cell and Ligament Fibroblast Responses on RGD-Modified Silk Fibers. *Journal of Biomedical Research* 67 :559–570 (2003).
- [207] Farokhi M, Mottaghitalab F, Fatahi Y, Khademhoseini A and Kaplan DL, Overview of Silk Fibroin Use in Wound Dressings. *Trends in Biotechnology* 36 :907–922 (2018).
- [208] Eming SA, Martin P and Tomic-Canic M, Wound Repair and Regeneration: Mechanisms, Signaling, and Translation. *Science Translational Medicine* 6 :265 (2015).
- [209] Liu T, Miao J, Sheng W, Xie Y, Huang Q, Shan Y and Yang J, Cytocompatibility of Regenerated Silk Fibroin Film: a Medical Biomaterial Applicable to Wound Healing. *Journal of Zhejiang University SCIENCE B* 11 :10–16 (2010).
- [210] Shan YH, Peng LH, Liu X, Chen X, Xiong J and Gao J, Silk Fibroin/Gelatin Electrospun Nanofibrous Dressing Functionalized with Astragaloside IV Induces Healing and Anti-Scar Effects on Burn Wound. *International Journal of Pharmaceutics* 479 :291–301 (2015).
- [211] Chutipakdeevong J, Ruktanonchai UR and Supaphol P, Process Optimization of Electrospun Silk Fibroin Fiber Mat for Accelerated Wound Healing. *Journal of Applied Polymer Science* 130 :3634–3644 (2013).
- [212] Grasset L, Cordier D and Ville A, Woven Silk as a Carrier for the Immobilization of Enzymes. *Biotechnology and Bioengineering* 19 :611–618 (1977).
- [213] Yoshimizu H and Asakura T, Preparation and Characterization of Silk Fibroin Powder and its Application to Enzyme Immobilization. *Journal of Applied Polymer Science* 40 :127–134 (1990).
- [214]. Lu S, Wang X, Lu Q, Hu X, Uppal N, Omenetto FG and Kaplan DL, Stabilization of Enzymes in Silk Films. *Biomacromolecules* 10 :1032–1042 (2009).
- [215]. Murphy AR and Kaplan DL, Biomedical Applications of Chemically-Modified Silk Fibroin. *Journal of Materials Chemistry* 19 :6443–6450 (2009).
- [216]. Lu S, Wang X, Uppal N, Kaplan DL and Li M, Stabilization of Horseradish Peroxidase in Silk Materials. *Frontiers of Materials Science in China* 3 :367–373 (2009).
- [217]. Demura M, Asakura T and Kuroo T, Immobilization of Biocatalysts with Bombyx Mori Silk Fibroin by Several Kinds of Physical Treatment and its Application to Glucose Sensors. *Biosensors* 4 :361–372 (1989).
- [218]. Chatterjee S, Barbora L, Cameotra SS, Mahanta P and Goswami P, Silk-Fiber Immobilized Lipase-Catalyzed Hydrolysis of Emulsified Sunflower Oil. *Applied Biochemistry and Biotechnology* 157 :593–600 (2009).
- [219]. Grasset L, Cordier D, Couturier R and Ville A, Immobilization of Alkaline Phosphatase on Silk Using Diazo, Adsorption, Glutaraldehyde, and Azide Method: Optimum pH and Properties of the Conjugates. *Biotechnology and Bioengineering* 25 :1423–1434 (1983).
- [220]. Tao H, Marelli B, Yang M, An N, Onses MS, Rogers JA, Kaplan DL and Omenetto FG, Inkjet Printing of Regenerated Silk Fibroin: From Printable Forms to Printable Functions. *Advanced Materials* 27 :4273–4279 (2015).
- [221]. Mehrotra S, de Melo BAG, Hirano M, Keung W, Li RA, Mandal BB and Shin SR, Myocardial Tissue Engineering: Nonmulberry Silk Based Ink for Fabricating Mechanically Robust Cardiac Patches and Endothelialized Myocardium-on-a-Chip Application. *Advanced Functional Materials* 30 :2070079 (2020).